

Phonon spectrum and soft-mode behavior of MgCNi₃

R. Heid¹, B. Renker¹, H. Schober², P. Adelmann¹, D. Ernst¹, and K.-P. Bohnen,¹

¹*Forschungszentrum Karlsruhe, Institut für Festkörperphysik,
P.O. Box 3640, D-76021 Karlsruhe, Germany and*

²*Institut Laue-Langevin, BP 156 X, F-38042 Grenoble Cedex, France*

(Dated: February 2, 2008)

Temperature dependent inelastic neutron-scattering measurements of the generalized phonon density-of-states for superconducting MgCNi₃, $T_c = 8$ K, give evidence for a soft-mode behavior of low-frequency Ni phonon modes. Results are compared with ab initio density functional calculations which suggest an incipient lattice instability of the stoichiometric compound with respect to Ni vibrations orthogonal to the Ni-C bond direction.

PACS numbers: 74.25.Kc, 63.20.Kr, 78.70.Nx, 74.70.Dd

The recent discovery of superconductivity near 8 K in MgCNi₃¹ was a surprise since due to the high Ni content a ferromagnetic ground state would have been expected rather than a superconducting one. Furthermore it is unusual that for this perovskite compound the heavy Ni atoms occupy the corners in Ni₆C octahedra. There are speculations that magnetic interactions might promote superconductivity², however, measurements of the specific heat come up with the conclusion that MgCNi₃ is a medium to strong coupling BCS superconductor^{3,4}. This compound bears similarity to superconducting nickel borocarbides where for the Y and Lu compounds an acoustic phonon branch exhibits a pronounced softening at lower temperatures^{5,6,7}, a feature which is supposed to be connected to superconductivity in these compounds. Hints for unusual lattice dynamical properties of MgCNi₃ have been inferred from a recent x-ray absorption study, which indicated deviations of the local atomic structure from the ideal perovskite lattice at temperatures below 70 K⁸, and from a very recent linear muffin-tin orbitals (LMTO) calculation of the harmonic phonons of MgCNi₃⁹, which found a dynamical instability of the stoichiometric compound. In this paper we will present inelastic neutron scattering (INS) measurements of the generalized phonon density-of-states (GDOS) as a function of temperature which show a softening of low-frequency Ni modes. We will compare our experimental results to ab initio density functional calculations.

For the synthesis of MgCNi₃ samples mixed powders of the components were pressed into pellets, wrapped into a tantalum foil, sealed in a quartz tube and heated for 2 h at 900°C. A difficulty arises from losses of volatile Mg and C at the synthesis temperature. With respect to subsequent x-ray analysis we obtained the best samples for a starting stoichiometry of Mg_{1.14}C_{1.4}Ni₃ where an impurity peak due to unreacted graphite was smallest. The T_c of our samples was 7.5 K. It could be slightly increased for the starting concentration C_{1.5} however at the expense of a somewhat larger contribution of unreacted graphite. Since the exact stoichiometry might be important for a soft-mode behavior which is found in the present investigation we show in Fig. 1 a x-ray diffraction pattern of our sample.

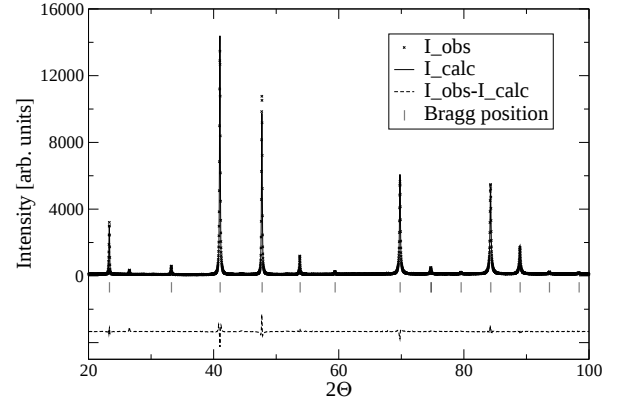


FIG. 1: Observed (crosses) and calculated (solid line) x-ray diffraction pattern for the investigated sample. A small impurity peak at 26.5° is due to unreacted graphite. The refinement ($R = 5\%$) yields a composition of MgC_{0.96}Ni₃ for the cubic perovskite structure, space group Pm3m, with lattice constant $a = 3.8085(1)$ Å and with positions of the atoms at: Mg 1a (0,0,0), C 1b (0.5,0.5,0.5), and Ni 3c (0,0.5,0.5).

Our INS measurements were performed at the HFR in Grenoble, France, on the IN6 and IN4 time-of-flight spectrometers. On IN6 a high chopper speed of 12060 rpm and focusing in the inelastic region were used to improve the resolution. Due to the low incident energy of 4.75 meV at this spectrometer which is connected to the cold source we profit from a very good resolution for low-energy excitations. The necessity to work in energy gain of the scattered neutrons sets limits on the possibility to work at lower temperatures. For example, for a sample temperature of 50 K we could follow excitations up to ~ 30 meV. The spectrometer is dedicated to inelastic measurements and a standard result is the GDOS which is calculated from the recorded intensities over a scattering region from 14° to 114° . For the data evaluation we have applied multi-phonon corrections in a self-consistent procedure¹⁰. The GDOS implies a weighting of vibrational modes by σ/m (scattering cross-section over the mass; we used values of 0.46, 0.179, and 0.31 barn/amu for C, Mg, and Ni, respectively). From a plot of the elastic intensities over momentum transfer we do not obtain

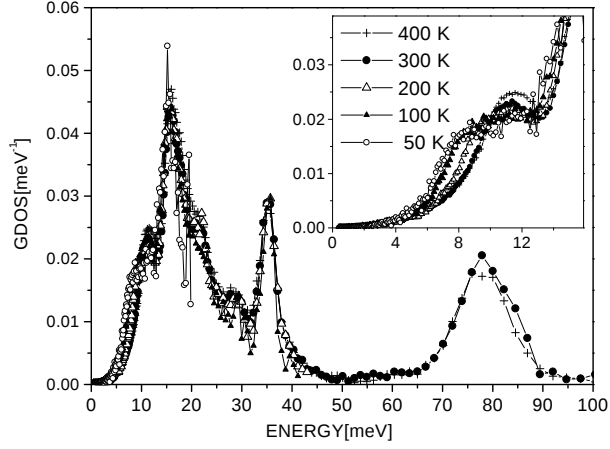


FIG. 2: The experimental generalized phonon density-of-states for MgCNi_3 . A significant soft-mode behavior is found for low-frequency Ni modes (insert).

any evidence for a structural phase transition within the investigated temperature region in agreement with previous results from structural investigations^{1,11}. However, due to the low incident energy this analysis is limited to $Q \leq 2.2 \text{ \AA}^{-1}$. To study changes in the dynamics in a larger temperature region, we have performed supplementary measurements with an incident neutron energy of 35 meV in the down-scattering mode over a wide range of temperatures on the instrument IN4. These results will be presented in the form of the dynamical susceptibility $\chi''(\omega)$ which is much closer related to the scattering function $S(Q, \omega)$ than the GDOS¹⁰.

Due to the large differences in mass the phonon spectrum of MgCNi_3 (Fig. 2) decomposes into two well separated parts, a low-frequency region with predominantly Ni and Mg modes and vibrations of the light C atom around 80 meV. From the known σ/m values and an analysis of the areas in the GDOS shown in Fig. 2 we find for the latter peak an almost perfect agreement between the theoretical and the experimental spectral weight implying contributions from three closely neighbored optical phonon branches. The weight of the sharp and well separated peak at 35 meV corresponds well to the weight expected for three optical Mg modes. It is increased by some 20% which suggests a small hybridization with the low-frequency Ni modes. The region below 33 meV contains exclusively Ni contributions. It is well structured and exhibits a very low frequency maximum at 12 meV and a strong main peak around 16 meV.

The 12 zone center optic phonons decompose according to $3F_{1u} + F_{2u}$ with no Raman active modes. Guided by investigations of the related system of quaternary borocarbides where a soft-mode behavior for superconducting $\text{RENi}_2\text{B}_2\text{C}$ ($\text{RE} = \text{Y, Lu}$) has been found we have measured the GDOS of MgCNi_3 for a series of temperatures between 400 K and 50 K. No changes are found for the peaks at 80 meV and 35 meV which were attributed to C and Mg vibrations (only a small sharpening of the

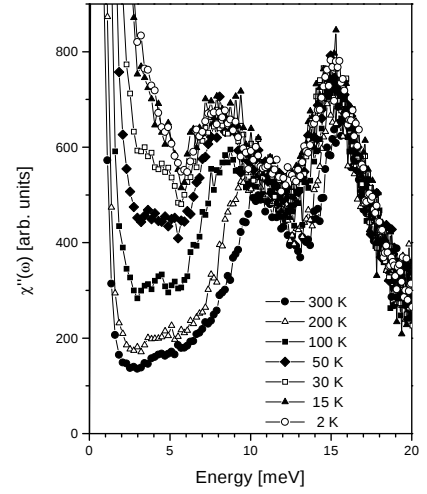


FIG. 3: The experimental dynamical susceptibility for MgCNi_3 (see text).

35 meV peak is registered). A pronounced softening, however, occurs for the very low-frequency part of the Ni vibrations in a region which is dominated by acoustic phonon branches. The insert in Fig. 2 shows a magnification. The strongest effect is observed between 200 K and 100 K. Only less pronounced changes occur between 100 K and 50 K which is the lowest temperature in our energy-gain measurements.

Changes in the dynamics show up clearer in the temperature evolution of $\chi''(\omega)$ in Fig. 3 where a sum of intensities recorded on IN4 for different scattering angles is shown. The incident neutron energy was chosen such that the low-energy region below 20 meV could still be studied with good resolution. The strong increase in intensity below 3 meV is due to elastic scattering contaminations. Whereas the frequency of the prominent Ni peak remains almost fixed at 16 meV we can observe the evolution of the soft-mode intensity. In agreement with the GDOS the strongest changes are observed around 100 K and only minor changes are recorded between 300 K and 200 K and between 30 K and 2 K. Additionally to the GDOS in Fig. 2 it can be seen that some intensity is shifted into the low-frequency region below 5 meV. While the increase in intensity below 10 meV is in general agreement with the mode softening a more detailed analysis of its location within the Brillouin zone (BZ) is not possible for this polycrystalline sample.

For an analysis of our data we have performed first principals density functional calculations using a mixed basis pseudopotential method. For Mg a well tested pseudopotential of Troullier-Martins type has been used^{12,13}, whereas for C and Ni Bachelet-Hamann-Schlüter type pseudopotentials were constructed¹⁴. The fairly deep d potential of Ni and p potential of C can be efficiently dealt with by the mixed-basis formalism, where the valence states are constructed from a combination of localized s and p functions at C sites and localized d functions

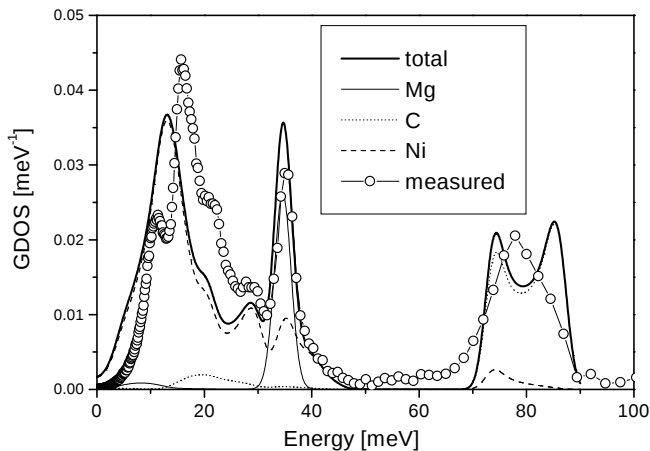


FIG. 4: Calculated GDOS spectra for stoichiometric MgCNi_3 . The proper σ/m values have been applied for a comparison to the experimental data (300 K spectrum). Contributions from an unstable phonon branch (see text) have been ignored.

at Ni sites, supplemented by plane waves up to a kinetic energy of 24 Ry. The local density approximation with the Hedin-Lundqvist parametrization of the exchange-correlation functional¹⁵ has been used. Our calculated electronic band structure is in good agreement with previous density functional studies^{2,16,17,18,19,20,21,22}. The most prominent feature of the electronic density-of-states is the existence of a strong and sharp van Hove peak less than 100 meV below E_F . It arises from antibonding bands related to the Ni d orbitals, which are very narrow due to the linear Ni coordination by C¹⁹.

Phonon dispersion curves for stoichiometric MgCNi_3 were calculated within the mixed-basis perturbation approach²³. Complete spectra are obtained from a Fourier interpolation of dynamical matrices calculated on a cubic ($4 \times 4 \times 4$) q-point mesh. Results for the optimized lattice constant $a=3.76 \text{ \AA}$ are depicted in Figs. 4 and 5. The theoretical GDOS (Fig. 4) reproduces many features seen in the experimental spectra, including the small maximum near 30 meV and the shoulder of the acoustic spectrum at 20 meV. The acoustic modes are predominantly of Ni character with only a small hybridization of C modes. The sharp peak near 35 meV arises from three almost dispersionless Mg branches with a small admixture of Ni vibrations.

The most prominent feature of the calculated dispersion curves (Fig. 5) is, however, the occurrence of unstable modes suggesting that the stoichiometric compound is dynamically unstable in the harmonic approximation. This instability appears over a large area in reciprocal space and is most pronounced near the zone boundary points X and M (with coordinates (100) and (110) in units of π/a , respectively). Inspection of the displacement vectors reveals that all unstable modes involve Ni vibrations orthogonal to the Ni-C bond directions. This behavior is most evident at the M point where the unstable mode represents a pure vibration of the Ni atoms with

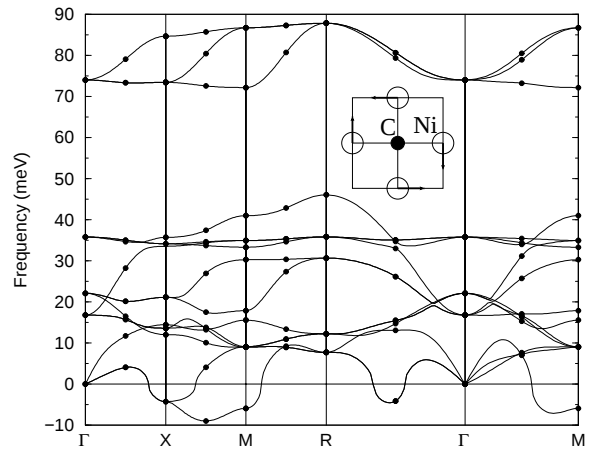


FIG. 5: Calculated phonon dispersion curves for stoichiometric MgCNi_3 for selected symmetry directions. Black circles denote the results from linear-response calculations. Lines are obtained by Fourier interpolation. Negative frequencies indicate unstable modes. At the M point, the unstable phonon corresponds to shear elongations of Ni atoms in the Ni-C planes as indicated in the insert.

all other atoms at rest. Its elongation pattern, shown in the insert of Fig. 5, induces shear distortions in the planar Ni-C sublattice. This extended phonon instability may be the origin of the apparent downshift of the acoustic part below 20 meV in the calculated spectrum by 3 meV with respect to the experimental one (see Fig. 4).

The presence of the van Hove peak close to E_F requires care in performing the BZ summations in the calculations. The presented results were obtained with cubic ($16 \times 16 \times 16$) Monkhorst Pack k-point meshes and a Gaussian broadening of 0.1 eV. Convergence studies showed that this is sufficient for most of the phonon modes to be converged within 0.5 meV, but the low-frequency Ni modes are more sensitive to the BZ sampling. Frozen-phonon studies of the unstable M-point mode using a variety of k meshes and Gaussian smearings have confirmed that this instability is not the result of an insufficient BZ sampling. Furthermore, a similar frozen-phonon calculation performed with the projector-augmented plane wave approach as implemented in the Vienna ab-initio simulation package (VASP-PAW)^{24,25,26,27} reproduced the instability, excluding the possibility that it is an artefact of the pseudopotential approximation.

An instability of Ni modes has been also found in a very recent ab initio investigation of the lattice dynamics and electron-phonon coupling (EPC) of MgCNi_3 using the LMTO method⁹. In contrast to our calculations, however, the instability did not appear at high-symmetry points at the BZ boundary. While both methods agree with respect to the frequency range for the Ni and C modes, the LMTO calculations predict significantly higher frequencies for the Mg modes (at $\approx 45 \text{ meV}$) at variance with our experimental and theoretical results.

The instability of the harmonic lattice dynamics of stoichiometric MgCNi_3 raises the question of the true low-temperature structure of this superconductor. Some insight can be gained from frozen-phonon studies for the unstable mode. For the shear mode at M we found a very shallow double-well potential, with a minimum of less than 1 meV at a displacement of only 0.025 Å. In the previous LMTO study, double-well potentials of similar magnitude have been extracted from frozen-phonon calculations corresponding to lower-symmetry points⁹. The shallowness of the double well suggests that the instability is not strong enough to induce a long-ranged structural distortion, but that the high-symmetry cubic structure is stabilized dynamically. The presence of strong anharmonic motions of atoms in the vicinity of a structural instability could be of relevance for superconductivity, as it may significantly enhance the EPC strength. For MgCNi_3 , a contribution of 37% coming from the anharmonic modes to the total EPC constant has been estimated on the basis of the LMTO results⁹. A complete calculation of the EPC strength, however, is a formidable task as it requires to take into account the full anharmonic lattice dynamics as well as anharmonic corrections to the EPC. This is further complicated by the fact that the local distortions are expected to strongly modify the van Hove singularity and thus the electronic structure in the vicinity of the Fermi energy⁹.

The picture of a dynamically stabilized cubic structure is consistent with published structural investigations

where no indications of any phase transition have been found, and with the temperature dependence of the elastic scattering intensity observed in our IN6 spectra. In a recent x-ray absorption fine structure measurement, an unusually broad Ni-Ni pair-correlation function has been observed below 70 K⁸. It was interpreted as the result of local distortions of the Ni octahedra predominantly perpendicular to the Ni-C bond with displacements of less than 0.05 Å, in agreement with the frozen-phonon results.

In conclusion, studies of the GDOS have provided a clear insight in the lattice vibrations of superconducting MgCNi_3 which can be looked at as a 3D analogue of the nickel borocarbides. For both kinds of compounds a remarkable soft-mode behavior in the low-frequency region (~ 8 meV) is observed. For the superconducting borocarbides where single crystals could be grown it was shown that the mode softening is restricted to a narrow region in reciprocal space and is sensitive to the formation of the superconducting gap⁷. In contrast, the present results suggest that the softening phenomena in MgCNi_3 is not directly linked to the superconducting state, but has its origin in an incipient dynamical instability of specific Ni vibrations which occurs widespread in reciprocal space. It cannot be excluded, however, that lattice defects play an important role in stabilizing the real structure. Further studies are required to clarify the question whether the apparently large stability range of the $\text{MgC}_{1-x}\text{Ni}_3$ phase is connected to the observed dynamical peculiarities.

-
- ¹ T. He, Q. Huang, A. P. Ramirez, Y. Wang, K. A. Regan, N. Rogado, M. A. Hayward, M. K. Haas, J. S. Slusky, K. Inumaru, H. W. Zandbergen, N. P. Ong, and R. J. Cava, *Nature* **411**, 54 (2001).
 - ² H. Rosner, R. Weht, M. D. Johannes, W. E. Pickett, and E. Tosatti, *Phys. Rev. Lett.* **88**, 27001 (2002).
 - ³ J.-Y. Lin, P. L. Ho, H. L. Huang, P. H. Lin, Y.-L. Zhang, R.-C. Yu, C.-Q. Jin, and H. D. Yang, *Phys. Rev. B* **67**, 052501 (2003).
 - ⁴ J.-Y. Lin and H. D. Yang, *cond-mat/0308198*.
 - ⁵ P. Dervénagias, M. Bullock, J. Zarestky, P. Canfield, B. K. Cho, B. Harmon, A. I. Goldman, and C. Stassis, *Phys. Rev. B* **52**, R9839 (1995).
 - ⁶ F. Gompf, W. Reichardt, H. Schober, B. Renker, M. Buchgeister, *Phys. Rev. B* **55**, 9058 (1997).
 - ⁷ J. Zarestky, C. Stassis, A. Goldman, P. Canfield, G. Shirane, and S. Shapiro, *Phys. Rev. B* **60**, 11932 (1999).
 - ⁸ A. Yu. Ignatov, L. M. Dieng, T. A. Tyson, T. He, and R. J. Cava, *Phys. Rev. B* **67**, 64509 (2003).
 - ⁹ A. Ignatov, S. Y. Savrasov, and T. A. Tyson, *cond-mat/0304466*.
 - ¹⁰ H. Schober, A. Tölle, B. Renker, R. Heid, and F. Gompf, *Phys. Rev. B* **56**, 5937 (1997).
 - ¹¹ Q. Huang, T. He, K. A. Regan, N. Rogado, M. A. Hayward, M. K. Haas, K. Inumaru, and R. J. Cava, *Physica C* **363**, 215 (2001).
 - ¹² N. Troullier and J. L. Martins, *Phys. Rev. B* **43**, 1993 (1991).
 - ¹³ G. Pelg, Dissertation, Universität Regensburg, unpublished.
 - ¹⁴ G. B. Bachelet, D. R. Hamann, and M. Schlüter, *Phys. Rev. B* **26**, 4199 (1982).
 - ¹⁵ L. Hedin and B. I. Lundqvist, *J. Phys. C: Solid St. Phys.* **4**, 2064 (1971).
 - ¹⁶ M. A. Hayward, M. K. Haas, A. P. Ramirez, T. He, K. A. Regan, N. Rogado, K. Inumaru, and R. J. Cava, *Solid. State Commun.* **119**, 491 (2001).
 - ¹⁷ A. Szajek, *J. Phys.: Condens. Matter* **13**, L595 (2001).
 - ¹⁸ S. B. Dugdale and T. Jarlborg, *Phys. Rev. B* **64**, 100508 (2001).
 - ¹⁹ D. J. Singh and I. I. Mazin, *Phys. Rev. B* **64**, 140507 (2001).
 - ²⁰ J. H. Shim, S. K. Kwon, and B. I. Min, *Phys. Rev. B* **64**, 180510 (2001).
 - ²¹ I. G. Kim, J. I. Lee, and A. J. Freeman, *Phys. Rev. B* **65**, 64525 (2002).
 - ²² I. R. Shein, A. L. Ivanovskii, and N. I. Medvedeva, *JETP Lett.* **74**, 122 (2001).
 - ²³ R. Heid and K.-P. Bohnen, *Phys. Rev. B* **60**, R3709 (1999).
 - ²⁴ G. Kresse and J. Hafner, *Phys. Rev. B* **47**, 558 (1993); *ibid.* **49**, 14251 (1994).
 - ²⁵ G. Kresse and J. Furthmüller, *Comp. Mat. Sci.* **6**, 15 (1996).
 - ²⁶ G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
 - ²⁷ G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).